

**The Response of Some SSNTD's to Alpha Energies in the Range
(1 to 5)MeV**

F.S.Al-Saleh and KH.A.Zarie

*Physics Department , Girls College of Education in Riyadh , Scientific
Departments
P.O.Box 27329 Riyadh 11417 Saudi Arabia*

Abstract

The variation of the response of four types of solid state nuclear track detector SSNTD's namely CR-39 , MK ,CN-85 and LR-115 as a function of etching time for different alpha energies have been studied. Alpha particles emitted from ^{239}Pu are used for track formation . The optimum condition of etching time for the four detectors are determined. The response of these detectors as a function of alpha energies at the optimum etching time conditions is obtained.

1. Introduction

The validity of various models of track formation may be judged by critical parameters such as charge , mass and energy of such incident particles as are able to form etchable tracks. Various authors [1-3] have suggested that the track formation should be related to a number of different parameters ,such as total energy loss rate ,primary ionization ,restricted energy loss ect..These track formation can be tested by irradiating a given solid with a number of ions at various energies and recording those cases for which etchable tracks are formed . If the track has been etched successively until the end of the ion range , it performs a cone with a tip point . The shape of the developed tracks in the plastic depends on the etching conditions. It goes through three phases namely conical , transition and spherical phases. Plastic track detectors are in use in diverse area of research such as radiation dosimetry, heavy ion physics, neutron physics, astrophysics, solar particles, geophysics and medicine [1-10] .These detectors consist of a long-chain organic molecules and have threshold for charged particle detection . Furthermore SSNTD's have some impressive features such as, they are cheap, simple in use, can be used in any space by any size and can be operated successfully in a wide range of fields [4 -12].

The aim of the present work is to study the optimum etching time and the induced changes in the response for each detector and its dependence on the alpha energies.

2. Experimental Techniques

2.1 Sample preparation for etching time measurements:

Different detectors of CR-39 (500 μm thickness) from pershore ltd, U.K, CN-85(100 μm thickness) and LR-115 (12 μm thickness) from Kodak pathe and Makrofal (MK) (300 μm thickness) from Bayer, Germany were used in this work. The size of each detector is 2.5x2.5 Cm.

To obtain the etching time at which we get the optimum response of SSNTD's, five groups from each type of detectors were used. The detectors were identified by numbering them on the upper right corners. LR-115 detectors were identified on the back support of the detectors. SSNTD were exposed to alpha-particles from a standard plutonium source ^{238}Pu (half-life 87.74 year) of activity 6.061×10^3 Bq manufactured by National Bureau of Standards U.S. Department of Commerce. The plutonium source was used with five collimators of lengths 5.7, 15.9, 24, 30.5 and 35.5 mm corresponding to alpha-particle energies 1,2,3,4,5 MeV respectively. These collimators were used also to obtain normally -incident alpha particles.

2.2 Counting technique:

The resulting alpha-tracks on each detector were counted under an optical microscope at a total magnification 400 \times . The number of alpha tracks per field was averaged over thirty fields counted for each detector and then the track density was obtained. The resulting data were used to study the relation between etching time and the response for each type of SSNTD's and at each energy of the alpha particles.

3. Results and Discussions

3.1 Characteristics of each SSNTD

3.1.1 Etching time

(a) CR-39:

Figures (1,a to e) show the variation of the response of CR-39 detectors as a function of the etching time for different alpha energies (1-5MeV) respectively, at etching conditions of 6.25N NaOH solution at 70°C[11].

From these figures we can see that the latent tracks on the detectors can not be revealed before three hours of etching. It is also seen that the response of the detectors is increasing with etching time until it reaches a certain value, then a plateau like shape is observed i.e. the response is independent on the etching time. It is clear that CR-39 detectors reach their maximum response for all alpha energies at etching time of 6 hours.

It can be concluded that 6 hours etching time in 6.25N NaOH solution at 70°C is enough for monitoring of alpha particles with energies in the range of 1-5MeV. To make the revealed tracks more clear especially for efficient monitoring of alpha particles of higher energies (alphas emitted by radon and its decay products), 8 hours etching time is suitable.

(b) Makrafol:

Figures (2,a to e) represent the variation of the response of MK detectors as a function of etching time for alpha energies (1-5MeV) in a solution of 45g H₂O + 40g C₂H₅OH + 15g KOH (or PEW solution) at 70°C[11]. From these figures it is noticed that 0.25 hour is enough for the 1MeV and 2MeV just to appear (revealed), but for higher energies (3-4MeV) it takes 0.5 hour and 0.75 hour for 5MeV. The response of MK detectors is maximum at 1.5h for alpha energies in the range 1-5MeV. At

F. S. Al-Saleh, et al ...

etching time higher than 1.5h, tracks of alpha energies 1MeV and 2MeV are start being overetched and the tracks became less clear. Therefore, the etching time for MK detectors should not exceed 1.5h at 70°C in the PEW solutions.

(c) CN-85 :

Figures (3,a to e) illustrate the variation of the response of CN-85 detectors as a function of etching time for the alpha energies 1-5MeV respectively in a 2.5N NaOH solution at 60°C[11]

Fig (3,a to d) shows that tracks of alpha energies 1,2,3and 4MeV respectively started to appear from 0.5h etching time while for 5MeV starting from 2h etching time. The response of CN-85 detectors for alpha-energies, 1-3MeV is constant over the time interval 0.5-3.5h. The response of CN-85 detectors at 4MeV and 5MeV alpha-energies reaches their maxima at 3h and remain constant till 4h. At etching time higher than 3h, tracks of 1MeV and 2MeV alpha-energies were over etched and became less clear. It can be then concluded that 3h etching time in a 2.5N NaOH solution is enough for efficient monitoring of alpha-particles with energies in the range 1-5MeV.

(d) LR-115:

The variation of the response of LR-115 detectors as a function of etching time for the alpha energies 1-5MeV respectively is shown in fig (4, a to e). The detectors were etched in a 2.5N NaOH solution at 60°C[11].

For 1MeV, at etching time < 2.5h reddish holes appeared in the red background of LR-115 because the range of 1MeV alpha-particle is small and more time of etching is needed (>2.5 h) to be white and can be counted. For alpha-particles with energies 2 and 3 MeV in (b) and (c), the tracks are revealed as white holes and can be counted after only 1.5h etching time.

The Response of Some SSND 'S ...

LR-115 detectors reach the maximum response for these energies at 2.5h etching time and tends to be constant at etching time > 2.5 h. In fig (4d) the tracks appear only after 2.5h. This phenomenon is attributed to the fact that the range of alpha-particles with energies > 4 MeV is greater than the thickness of the thin layer of LR-115 and the linear energy transfer (LET) decreases with increasing energy of alpha particles. For 5MeV alpha particles the tracks are apparent after 3h etching time. In general, the optimum etching time for the LR-115 detectors in 2.5N NaOH solution at 60°C is 3h for all energies of alpha particles to be detected. Table (1) represents the optimum conditions of etching for the four mentioned detectors CR-39 , MK , CN-85 and LR-115.

Table (1) : Etching solutions and optimum etching conditions for the four types of SSNTD ; CR-39, MK, CN-85 and LR-115.

Detector type	Optimum conditions			
	Etching solution	Normality (N) [11]	Temperature °C [11]	Etching time (h) this work
CR-39	NaOH	6.25	70	8
MK	45g H ₂ O+40g C ₂ H ₅ OH+15g KOH		70	1.5
CN-85	NaOH	2.5	60	3
LR-115	NaOH	2.5	60	3

3.1.2 Energy-Response:

Figures (5,a to d) illustrate the variation of the response of CR-39, MK, LR-115 and CN-85 respectively as a function of alpha energies at the optimum etching conditions of each detector. The

response of MK detectors decreases slightly with a linear relationship over the energy range 1-4MeV. At higher energies, the response decreases sharply. The response of (CN-85 and LR-115) detectors is constant over the energy range 1-4MeV and the response of these detectors decreases sharply with alpha energies higher than these values.

The response of CR-39 detectors conserves the linearity of decrease with increasing alpha energies over the entire energy range 1-5MeV. This means that the response of CR-39 detectors at energies > 4MeV is higher than that of the other three detector types MK, CN-85 and LR-115. In general, MK detectors are found to have the highest response in the energy range 1 to 5 MeV.

Acknowledgment: The authors are extremely thankful to prof. S.A. El Fiki, Girls College, for her help and constant encouragement.

References

- [1] Fleisler R.L., Price B. and Walker R.M. "*Nuclear Tracks in Solids, Principles and Applications*". University of California press, Berkeley (1975).
- [2] Nagp K.K. "*Recent Research in Geology*". Hindustan publishing, New York (1974) 41.
- [3]. Durrani S.A and Bull R.K, "*Solid state nuclear track detection Principles*", *Methods and Applications*, pergamon press, oxford, (1987)
- [4] El-Fiki S.A., Kenawy M.A., Eissa H.M., Sharaf M.A., El Fiki M.A. and Abdel Hady M.L., "CR-39 and LR-115 as a Secondary Standard Dosimeter for Radon Dose Calibration". *Nucl. Tracks Radiat. Meas.*, 22,4, (1993) 323-325
- [5] A.J.Khan "Calibration of a CR-39 Plastic Track Detector for the Measurement of Radon and its Daughters in

The Response of Some SSND 'S ...

- Dwellings" *Nucl. Tracks Radiat. Meas.*,17,4,(1990)497-502.
- [6] Durrani S.A.,and James K.“The Effect of Irradiation Temperature on the Registration and Annealing Properties of Nuclear Tracks in Plastic” *Nucl.Track Radiat. Meas.*,15,1-4(1988)223-230.
- [7] Sing B.and Virk H.S., “Effect of Soil and Sand Moisture Content on Radon Diffusion Using Plastic Track Etch Detector” *Nucl.Track Radiat. Meas.*,26,1-4(1995)49-50.
- [8] Somogyi G.,Proc. 11th Intern. Conf. On SSNTD. Bristol, Supplement No.3,Nucl. Tracks.Oxford; Pergamon Press(1982)101.
- [9]Somogyi G. and Hunyadi I., Proc. 10th Intern. Conf. on SSNTD,Lyon,Pergamon Press,Oxford,England,(1979)443.
- [10] EL-Fiki M.A.,EL-Fiki S.A.,Sharaf M.A.,Eissa H.M. and Hassan G.M.“Autoradiographic Measurements of Low Concentration of Alpha Active Nucleides Using CR-39 Track Detector” *Nucl.Tracks Radiat. Meas.*,22,1-4(1993)863-866.
- [11]EL-Husseiny H.M.,“ Radiation Dose Measurements Using Solid State Detectors”,Ph.D.Thesis,Faculty of Science Ain Shams Univ. (1996).

F. S. Al – Saleh, et al ...

دراسة استجابة بعض كواشف الاثر النووي للطبقة لجسيمات الفا ذات الطاقة (1-5) م.ا.ف

فردوس سعود الصالح ، خديجه علي زارع

قسم الفيزياء ، كلية التربية للبنات بالرياض / الأقسام العلمية

ص.ب. ٢٧٣٢٩ الرياض ١١٤١٧ المملكة العربية السعودية

المخلص العربي

تم في هذا البحث دراسة استجابة كواشف الاثر النووي لجسيمات الفا ذات الطاقة من ١ الى ٥ م.ا.ف. و وجد أن ظروف الحفر المثلى للكواشف المستخدمة في محلول هيدروكسيد الصوديوم ذو عيارية ٢٥ || ٦ عن ٧٠ م هي ثماني ساعات لكواشف س ر-٣٩ وفي محلول PEW عند ٧٠ م لمدة ساعة ونصف لكواشف الماكرو فول ، أما بالنسبة لكواشف س ن-٨٥ و كواشف ل ر-١١٥ فان ظروف الحفر المثلى في محلول هيدروكسيد الصوديوم ذو لعيارية ٢٥ || ٦ عند ٦٠ م هي ثلاث ساعات ، كما وجد أن كواشف س ر-٣٩ أعطت اعلى إستجابة لطاقات الفا الأعلى من ٥ م.ا.ف

The Response of Some SSND 'S ...

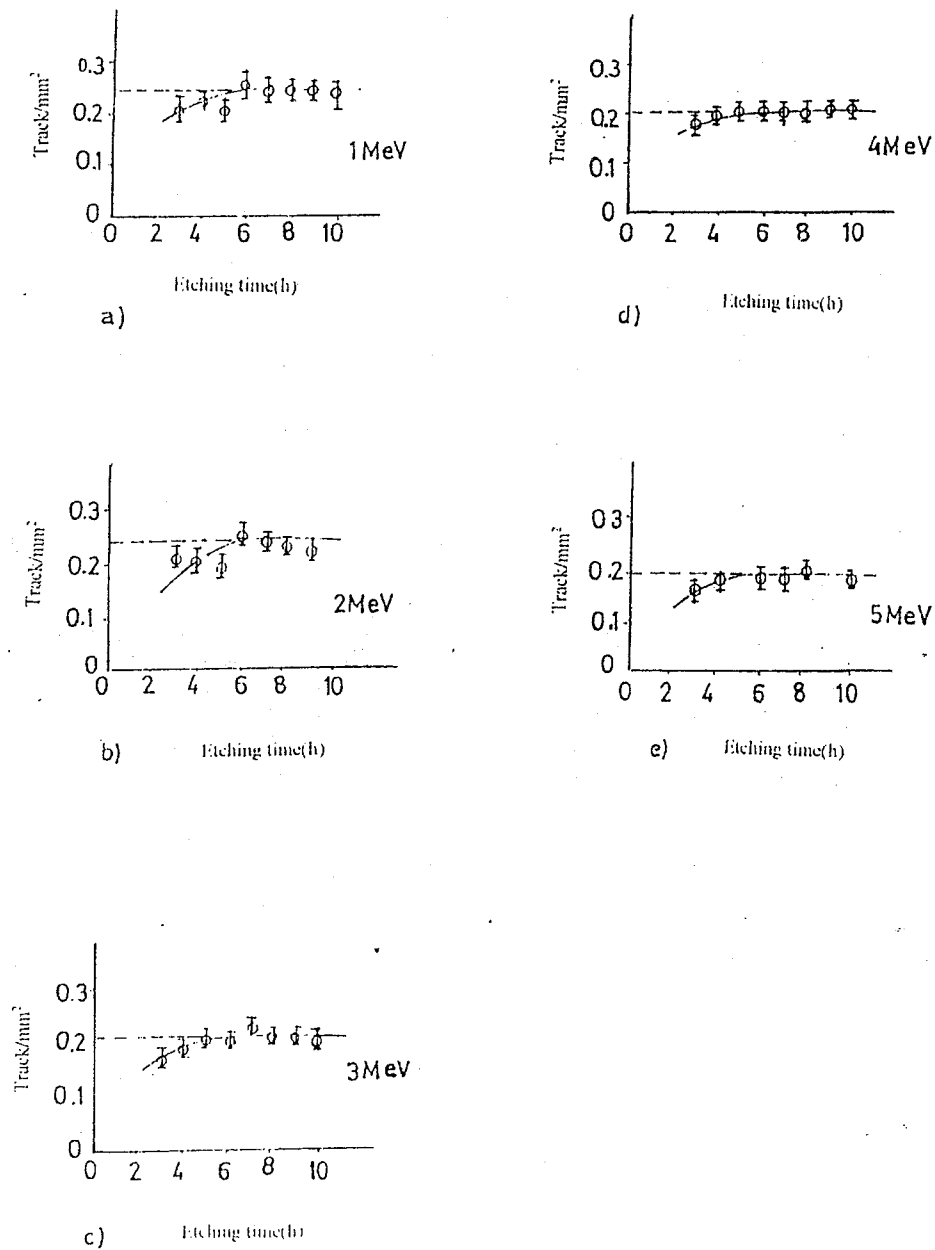


Fig. (1.a to e) : Variation of the response of CR-39 detectors for different, alpha-energies. Etching condition : 6.25N NaOH solution at 70°C.

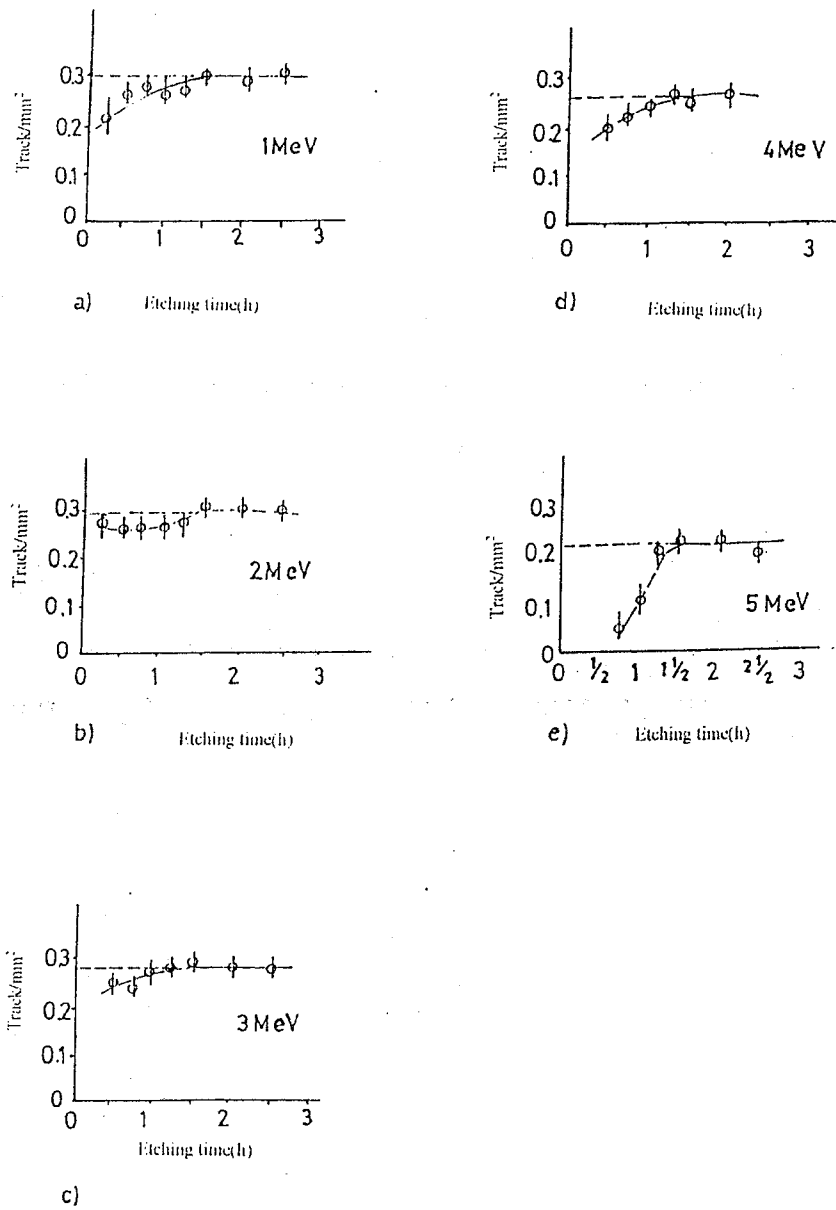


Fig. (2, a to e) Variation of the response of MK detectors for different alpha-energies. Etching condition: PEW solution at 70 °C.

The Response of Some SSND 'S ...







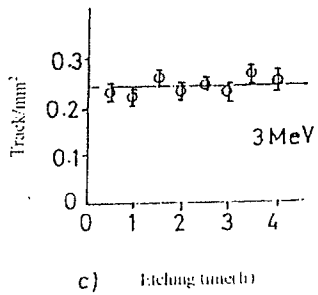



Fig. (3, a to e): Variation of the response of CN-85 detectors for different alpha-energies. Etching condition : 2.5N of NaOH solution at 60°C.

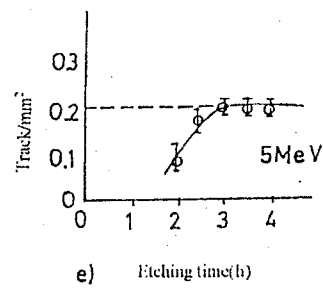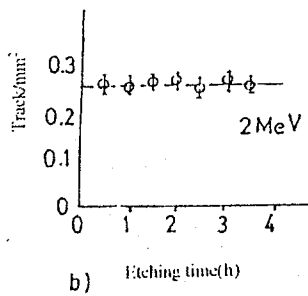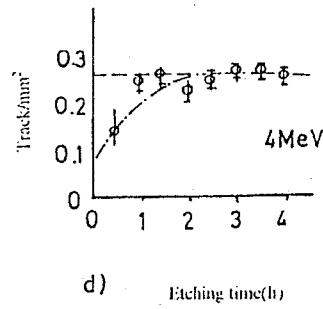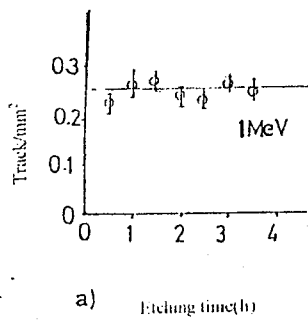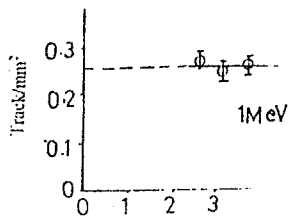


a) Etching time(h)

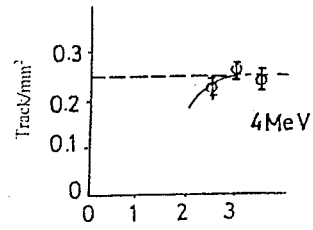


d) Etching time(h)

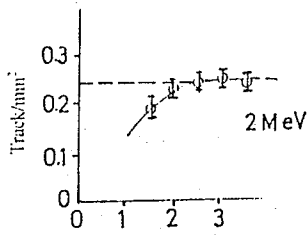

b) Etching time(h)

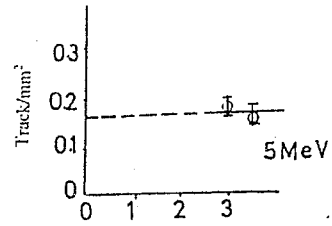


e) Etching time(h)

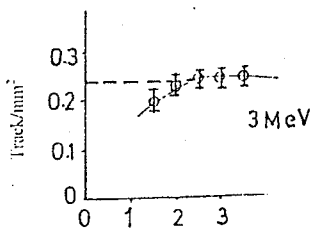


c) Etching time (h)

Fig. (4, a to e) : Variation of the response of LR-115 detectors for different alpha-energies. Etching condition : 2.5N NaOH solution at 60°C.


The Response of Some SSND 'S ...

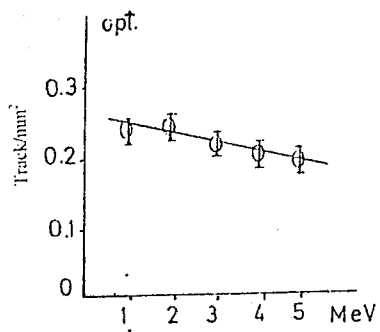


a. CR 39

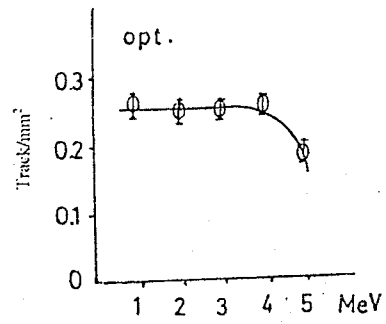

c. LR -115

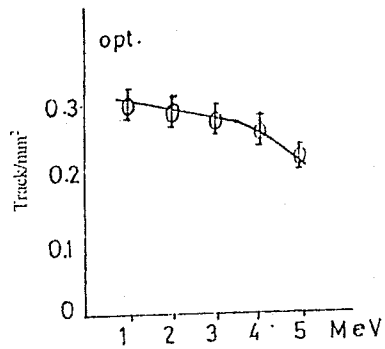

b. MK

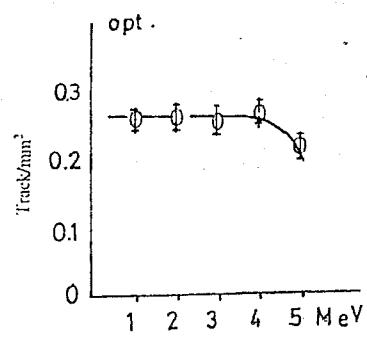

d. CN - 85

Fig 5: Variation of the response of a) CR-39, b) MK, c) LR-115 and d) CN-85 track detectors for alpha-energies in the range 1-5MeV at optimum etching condition of each detector.